



CLIENT: International Cellulose Corporation
P.O. Box 450006
Houston, TX 77245-0006

Attn: Joe Witt

Test Report No: 177770-R	Date: August 13, 2003
---------------------------------	------------------------------

SUBJECT: ASTM C518 Thermal Conductivity of Cellulose Insulation.

SAMPLE ID: One sample of Sprayed Cellulose Fiber Insulation was received from the client on 6/16/03. The sample was received in good condition.

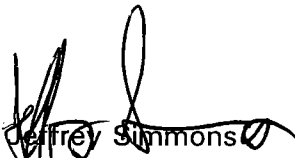
PROCEDURE: The cellulose insulation was tested in accordance with ASTM C518. No revisions to this report will be allowed after 90 days of the report date.


TEST DATE: 6/20/03.

RESULTS: Test results are on the following page(s).

CERTIFICATION: The tests reported here were conducted under the continuous direct supervision of SGS U.S. Testing Company Inc., Tulsa, OK.

**SIGNED FOR AND ON BEHALF OF
SGS U.S. TESTING COMPANY INC.**


bk Jeffrey Simmons
Manager Laboratory Operations


Dale E. Holloway
Branch Manager Laboratory Operations

This report is issued by SGS U.S. Testing Company Inc. under its General Conditions for Testing Services, as printed on reverse side. SGS U.S. Testing's responsibility under this report is limited to proven negligence and will in no case be more than the amount of the testing fees. Except by special arrangement, samples are not retained by SGS U.S. Testing for more than 30 days. The results shown on this test report refer only to the sample(s) tested unless otherwise stated, under the conditions agreed upon. Anyone relying on this report should understand all of the details of the engagement. Neither the name, seals, marks nor insignia of SGS U.S. Testing may be used in any advertising or promotional materials without the prior written approval of SGS U.S. Testing. The test report cannot be reproduced, except in full, without prior written permission of SGS U.S. Testing Company Inc.



Test Procedure and Results

T Hot (°F)	T Cold (°F)	Avg. Hot/Cold Face Temperature	Thickness (inch)	Thermal Conductivity Btu-in/hr-ft ² -°F	Thermal Resistance Hr-ft ² -°F/Btu	Thermal Resistance per in. Hr-ft ² -°F/Btu/in.
98.31	50.59	74.45	0.799	0.255	3.1	3.88
98.30	50.60	74.45	0.799	0.255	3.1	3.88
98.29	50.59	74.44	0.799	0.255	3.1	3.88
98.27	50.59	74.43	0.799	0.255	3.1	3.88

End of Report